

TECHNICAL DATA SHEET

KEXCELLED THE K7™ PET CF10

Product code:	Revision Number:	Revision date:	TDS No.:
THE K7™ PET CF10	06	20/02/2025	KT037

Characteristic:

Environmentally friendly|good interlayer bond|no buckling deformation.

IDENTIFICATION OF THE MATERIAL

Trade name	THE K7™ PET CF10
Chemical name	Carbon fiber reinforced polyethylene terephthalate
Use	3D Printing
Origin	KEXCELLED

GUIDELINE FOR PRINT SETTINGS

Nozzle temperature	250~290℃
Bed temperature	90~110℃
Bed modification	Tape or glue
Active cooling fan	0%~50%
Layer height	0.2mm
Shell thickness	≥0.8mm
Print speed	≤200mm/s

Settings are based on a 0.4mm nozzle.

MATERIAL PROPERTIES

		Test Method
Melt flow rate (MFR) ¹	60~70g/10min	ISO 1133
Heat deflection temperature(HDT) ²	80℃	ISO 75
Vicat softening temperature(VST) ³	102℃	ISO 306
density	1.32~1.34g/cm ³	ISO 1183
Odor	Odorless	/
Solubility	Insoluble in water	/

1.test conditions: T= 270℃; m= 1.2kg.

2. test conditions:0.45MPa;120℃/h.

3. test conditions:10N; 120℃/h.

MECHANICAL PROPERTIES|TENSILE TEST
Test Method ISO 527

All test specimens were printed using a BambuLab X1C under the following conditions:


Printing temperature: 270°C

Heated bed temperature: 100°C

Print speed: 100mm/s

Shell thickness: 1.2mm

Infill under Concentric circles

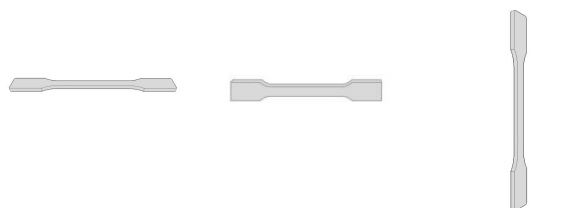


	Printed horizontal X,Y-axis	Printed horizontal X,Z-axis	Printed horizontal Z,X-axis ^{1,2}
Infill	100%	100%	100%
Tensile strength (Mpa)	80~100	113~118	21~25
Elongation at break (%)	4~8	5~8	3~6
E modulus (Mpa)	6400~6900	8400~8700	1600~1800

MECHANICAL PROPERTIES|IMPACT TEST
Test Method ISO 179

The same conditions as tensile test.

1→impact direction




Infill	100%	100%	100%
Impact strength (KJ/m ²)	14~20	17~22	3~9
Notch impact strength ³ (KJ/m ²)	4~6	5~8	1~3

MECHANICAL PROPERTIES |FLEXURAL TEST
Test Method ISO 178

The same conditions as tensile test.

1→bending direction

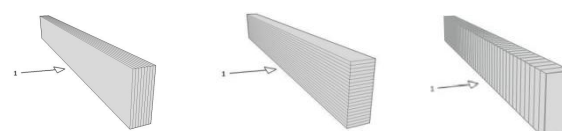

Infill	100%	100%	100%
Maximum force (Mpa)	129~147	195~200	41~46
Flexural modulus (Mpa)	3500~4400	7000~7900	1300~1600

1. Z,X-axis test data are for reference only

2. the stress range of the Z,X-axis modulus: 1~5MPa

3. notch type: type A

FILAMENT SPECIFICATION		Test Method
Diameter 1.75mm	1.75±0.03mm	EX1125
Max roundness deviation (1.75)	0.03mm	EX1125
Net weight on reel	1kg	EX1125